arXiv:0904.3512v2 [cond-mat.supr-con] 2 May 2009

Possible strong electron-lattice interaction and giant magneto-elastic effects in Fe-pnictides

Miodrag L. Kulić[1] and Amir A. Haghighirad[2]

[1] *Goethe-University Frankfurt, Theoretical Physics, 60054 Frankfurt/Main, Germany*
[2] *Goethe-University Frankfurt, Institute of Physics, 60054 Frankfurt/Main, Germany*

PACS `74.25.Jb` –
PACS `74.25.Kc` –
PACS `74.70.Dd` –

Abstract. - The possibility for an appreciable many-body contribution to the electron-phonon interaction (EPI) in Fe-pnictides is discussed in the model where EPI is due to the electronic polarization of As- ions. The polarization induced EPI_{pol} potential V_{ep} is large for vibrations of the As-ions and depends strongly on the As-Fe distance d, i.e. $V_{ep} \sim d^{-4}$. The EPI_{pol} coupling g_{ep}^{pol} is much larger than the one obtained in the LDA band structure calculations, with $g_{ep}^{pol}(\sim 16$ $eV/\mathring{A}) \gg g_{ep}^{(LDA)}(< 1\ eV/\mathring{A})$ and the bare pairing EPI_{pol} coupling constant $\lambda_{ep,A_{1g}}^{0} \sim 1$. It contributes significantly to the intra-band s-wave pairing and an appreciable positive As-isotope effect in the superconducting critical temperature is expected. In the Fe-breathing mode the linear (in the Fe-displacements) EPI_{pol} coupling vanishes, while the non-linear (quadratic) one is very strong. The part of the EPI_{pol} coupling, which is due to the "potential" energy (the Hubbard U) changes, is responsible for the giant magneto-elastic effects in MFe_2As_2, $M = Ca$, Sr, Ba since it gives much larger contribution to the magnetic pressure than the band structure effects do. This mechanism is contrary to the LDA prediction where the magneto-elastic effects are due to the "kinetic" energy effects, i.e. the changes in the density of states by the magneto-elastic effects. The proposed EPI_{pol} is expected to be operative (and strong) in other Fe-based superconductors with electronically polarizable ions such as Se, Te, S etc., and in high-temperature superconductors due to the polarizability of the O^{2-} ions.

Introduction. – Recently, superconductivity (SC) with high critical temperature T_c was discovered in several families of Fe-pnictides. In the electron (e) doped (1111) system $LaFeAsO_{1-x}F_x$ one has $T_c \approx 26\ K$ (and 43 K at high pressure) [1]. The record values are $T_c \approx 55\ K$ in $SmFeAsO_{1-x}F_x$ [2] and $T_c \approx 56$ K in $Sr_{1-x}Sm_xFeAsF$ [3], etc. In the hole (h) doped (122) system $Ba_{0.6}K_{0.4}Fe_2As_2$ one has $T_c = 38\ K$ [4]. Other families are reported, such as $MFeAs$ with $M = Li, Na$ and $T_c = 18\ K$, and the binary systems $Fe(Te, Se)$ with $T_c < 12\ K$. A common phase diagram has emerged with: (i) the structural transition appears around $T_{str} = (140-200)$; (ii) the SDW-type magnetic ordering occurs at $T_{sdw} \leq T_{str}$, while superconductivity appears when the SDW ordering vanishes. The latter can be done either by e- or h-doping or by applying high pressure.

The important question is - what is the pairing mechanism in Fe-pnictides? The vicinity of these systems to the antiferromagnetic phase was inspiration for spin fluctuation (SF) pairing models with *repulsive interaction* in the s-wave channel. This line of thinking was encouraged by the small electron-phonon coupling λ_{ep} obtained in the LDA band structure calculations for $LaO_{1-x}F_xFeAs$ [5], with $\lambda_{ep}^{LDA)} \sim 0.2$ and $T_{c,ep}^{(LDA)} \sim 1\ K$. However, this repulsive interaction in the singlet channel might be effective only if the coupling constant for the scattering of pairs from the hole to the electron-band - the $hh \leftrightarrows ee$ scattering, is much larger than the intra-band (repulsive) couplings, i.e. $\left|\lambda_{he}^{sf}\right| \gg \left|\lambda_{hh}^{sf}\right|, \left|\lambda_{ee}^{sf}\right|$. In that case the $s_{\pm}$ superconductivity is realized, where the gaps on the h- and e- Fermi surfaces exhibit opposite signs, $sign(\Delta_h) = -sign(\Delta_e)$ [6]. An indirect experimental support for $s_{\pm}$ pairing would be existence of an very pronounced resonance peak in the dynamical spin susceptibility [7] $Im\chi(\omega, \mathbf{Q})$ at $(\omega/2\Delta_0) \sim 0.6$ and at the SDW wave vector $\mathbf{Q}$. The experimental situation is at present unclear since in $LaO_{0.87}F_{0.13}FeAs$ [8] this peak is not observed, while in [9] it is observed but not very pronounced. However, several recent NMR measurements of the T_1-relaxation rate in $LaO_{1-x}F_xFeAs$, if confirmed, disfavor the SF scenario. First, in [10] it is reported that T_1-relaxation rates on the nuclei ^{139}La, ^{57}Fe, ^{75}As in $LaO_{1-x}F_xFeAs$ scale with one another, in spite of different form factors in the q-space. This means a lack of any pronounced q-structure in $Im\chi(\omega,\mathbf{q})$, thus disfavoring the SF pairing mechanism which assume that $Im\chi(\omega,\mathbf{q})$ is strongly peaked at $Q=(1/2,1/2)$. Second, by increasing doping x in $LaFeAsO_{1-x}F_x$ $(0.04 \leq x \leq 0.14)$ the T_1-relaxation rate of ^{75}As decreases by almost two orders of magnitude, while T_c is practically unchanged [11], thus again disfavoring the SF scenario. However, these experiments do not exclude the first order direct Coulomb interaction as the inter-band pairing mechanism. In order to increase T_c in a multi-band system the *intra-band pairing* should contribute positively to T_c. This may happen if the intra-band pairing potentials are: (a) attractive - giving rise to a conventional s-wave pairing, or (b) repulsive and anisotropic - giving rise to an unconventional pairing. In the latter case the system is very sensitive to the presence of nonmagnetic impurities. The $s_{\pm}$ pairing is also sensitive to nonmagnetic impurities although in some occasions they are less detrimental than for unconventional pairing. For instance, in the unitary limit $s_{\pm}$ is unaffected while in the Born limit these impurities are pair-breaking for it [12], [13]. The analysis of the resistivity $\rho(T)$ [13] and the upper critical field $H_{c2}(T)$ [14] gives evidence for appreciable impurity effects in single crystals of the Fe-pnictides, which disfavor any gapless unconventional pairing [13]. The same analysis hints that the *attractive intra-band pairings*, with $\lambda_{hh}, \lambda_{ee} > 0$, are important in the Fe-pnictides which can be only due to EPI or to an excitonic mechanism [13].

The above results imply a reconsideration of the role of EPI in the Fe-pnictides. This is supported by the recent neutron scattering experiments where the structural properties of the Fe-pnictides are sensitive to the magnetic order by showing *giant magneto-elastic effects.* For instance, in $CaFe_2As_2$ there is a first-order phase transition from the orthorhombic to the tetragonal structure under the pressure $P_c > 0.35\ GPa$, while at the same time the magnetic order vanishes [15]. Concerning the role of EPI in these materials there were recently two controversial reports: the first one on a *positive* and *large Fe-isotope effect* in T_c, and surprisingly also in T_{sdw}, for the substitution $^{56}Fe \rightarrow ^{54} Fe$ in $SmFeAsO_{1-x}F_x$ and $Ba_{1-x}K_xFe_2As_2$ with $\alpha_{Fe}^{(T_c)} \approx 0.33-0.4$ and $\alpha_{Fe}^{(T_{sdw})} \approx 0.35-0.4$ [16]. The second one [17] reports, contrary to the first one, on a *negative Fe-isotope effect* with $\alpha_{Fe}^{(T_c)} = -0.18$.

These results point to a rather strong involvement of EPI in magnetic, elastic and in superconducting properties of Fe-pnictides and to the importance of many-body effects. In the following we discuss a possibility for a many-body EPI channel in the Fe-pnictides, which is due to the *large electronic polarizability of the As-ions* - we call it EPI_{pol}. The importance of the electronic polarizability of the ligands in the screening of the core electrons in the excitonic spectra of halides and oxides was first recognized and studied by the Sawatzky group in [18] and later on applied on the Mott-Hubbard model for the screening of the (on-site) atomic Coulomb repulsion by the fast electronic polarizability processes [19] - we call it the SPS model (the Sawatzky polarization screening model). The SPS model was recently applied to the Fe-pnictides [20] where the relatively small Hubbard repulsion on Fe-ions was explained by the screening via the huge electronic polarizability of the As-ions. Here we argue that if the SPS model is realized in the Fe pnictides then it gives rise inevitably to: (i) the large EPI_{pol} potential V_{ep} for vibrations of the As-ions (especially in the As A_{1g}-modes); (ii) the strong dependence of V_{ep} on the $As-Fe$ distance d_{As-Fe} with $V_{ep} \sim d^{-4}_{As-Fe}$. As the consequence, the EPI_{pol} coupling $g_{ep}(= \partial V_{ep}/\partial d_{As-Fe})$ is much larger than the the LDA values since $g_{ep}(\sim 20\ eV/\AA) \gg g_{ep}^{(LDA)}(< 1\ eV/\AA)$, thus giving an appreciable contribution to the bare EPI_{pol} coupling constant $\lambda^0_{ep,A_{1g}} \approx 1$. The latter may significantly contribute to the intra-band s-wave pairing, thus disfavoring any gapless unconventional intra-band pairing. In the case of EPI_{pol} an appreciable positive *As-isotope effect* in T_c is expected. Furthermore, EPI_{pol} may be responsible for the giant magneto-elastic effects in MFe_2As_2, $M = Ca$, Sr, Ba . In that sense we construct the thermodynamic potential $G(S_Q,\varepsilon,P)$ as a function of the strain ε, the SDW magnetic order parameter S_Q and the pressure P by taking into account the effects of EPI_{pol}. Based on this, we argue that the giant magneto-elastic effects in MFe_2As_2, $M = Ca$, Sr, Ba are dominated by EPI_{pol}, since it gives much larger contribution to the magnetic pressure than that predicted by LDA [22], [23], [24].

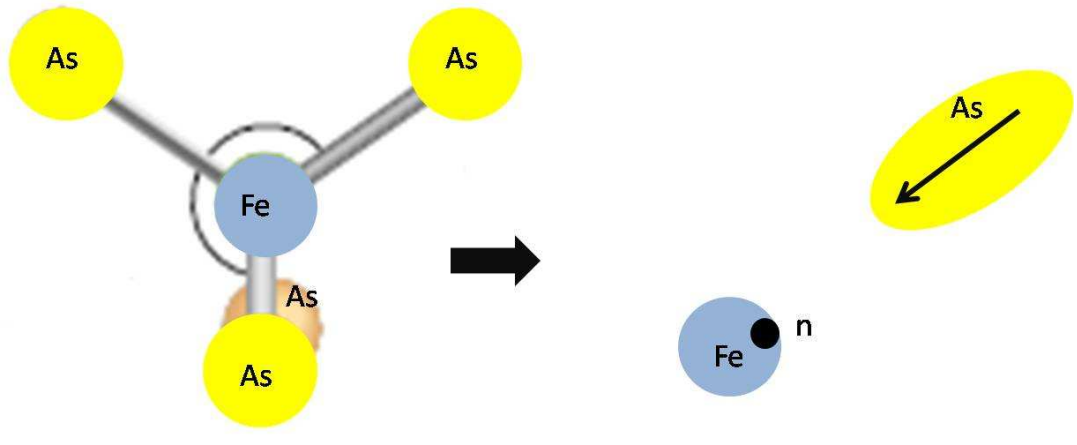

Fig. 1: Schematic picture of the polarization of the As electronic cloud due to charge fluctuations (n) on the Fe-ions. The tiny arrow on the As-ion describes the induced electronic dipole moment on As.

EPI due to the As electronic polarizability. – The electronic part of the Hamiltonian in the SPS model applied to the Fe-pnictides contains several many-body effects, i.e. $\hat{H} = \hat{H}_{0,e} + \hat{H}_c + \hat{H}_H^{at} + \hat{H}_{core}$. Here, $\hat{H}_{0,e}$ is the kinetic energy of the conduction electrons, $\hat{H}_c$ their long-range Coulomb interaction, while the Hubbard term

$\hat{H}_H^{at}$ describes the *unscreened (on-site) atomic repulsion* U_{at} on the Fe-ions. $\hat{H}_{core}$ describes the (very) polarizable electronic cores of the As-ions. Fluctuations of charges on the Fe-ions create an electric field on the As-ions which induces the polarization $\mathbf{P}_{As}$ of their cores, thus lowering the energy of the system - see Fig.1. By eliminating the core degrees of freedom the part $H_H^{at} + \hat{H}_{cor}$ can be approximated by the Hamiltonian $\hat{H}^{(pol)} = \hat{H}_0^{(pol)} + \hat{H}_H^{(pol)} + \hat{H}_c^{(pol)}$ - see more in [18]- [20]. This is pure many-body effect and almost not captured by the LDA band structure calculations. Applied to the Fe-pnictides it gives

$$\hat{H}_0^{(pol)} = -\sum_{\mathbf{R}_{Fe}} V_P(\mathbf{R}_{Fe})\hat{n}_{\mathbf{R}_{Fe}}/2, \qquad (1)$$

which renormalizes the local energy on the Fe-ions.

What is important for the magnetic and magneto-elastic properties is tha this polarization process *renormalizes also the Hubbard on-site repulsion* giving $\hat{H}_H^{(pol)}$

$$\hat{H}_H^{(pol)} = \sum_{\mathbf{R}_{Fe}} U^{(sc)}_{\mathbf{R}_{Fe}} \hat{n}_{\mathbf{R}_{Fe}\uparrow}\hat{n}_{\mathbf{R}_{Fe}\downarrow}, \qquad (2)$$

with the *screened Hubbard repulsion* $U^{(sc)}_{\mathbf{R}_{Fe}} = U_{at} - V_p(\mathbf{R}_{Fe})$; $\mathbf{R}_{Fe}$ enumerates the Fe-ions. The screening term $V_p(\mathbf{R}_{Fe})$, which is due to the *electronic polarizability* of the As-ions, is given in the point charge approximation by [20]

$$V_p \approx \sum_{\mathbf{R}_{As}\epsilon n.n.\mathbf{R}_{Fe}} \frac{\alpha_{As}e^2}{|\mathbf{R}_{Fe}-\mathbf{R}_{As}|^4}, \qquad (3)$$

where $\mathbf{R}_{As}$ enumerates the As-ions which are nearest neighbors ($n.n.$) of a given Fe-ion and α_{As} is the electronic polarizability of the As-ion. The physical picture behind the term $V_p(\equiv 2E_p)$ is the following: the charge fluctuations on the neighboring Fe-ions cause local electric fields $\mathbf{E}_{loc,As}$ on the As-ions, where $\mathbf{E}_{loc,As}$ polarizes the As electronic clouds by exciting s-p transitions as shown schematically on Fig.1. The induced dipole moments lower the energy by an amount $E_p \approx \alpha_{As}\sum_{R_{As}}\mathbf{E}^2_{loc,R_{As}}/2$. Due to large α_{As}, with $\alpha_{As} \sim (10-12)$ $\mathring{A}^3$one obtains $V_p \sim 10$ eV [20]. Since $U_{at} < 15e$ V it gives $U^{(sc)} \lesssim 3$ eV. Since $U^{(sc)}$ is comparable to the band-width W this means that the Fe-pnictides are in a moderately correlated regime.

The meaning of $U^{(sc)} = U_{at} - V_p$ and V_p can be understood by the following analysisc [18]- [20]. The Hubbard repulsion U in solids is the difference between the ionization energy I and the electron affinity A, i.e. $U^{(sc)} = I - A$. In solids the atomic ionization energy is lowered by E_p while the atomic electronic affinity is increased by E_p, i.e. $U^{(sc)} = I - A = (I_{at}-E_p) - (A_{at}+E_p) = U_{at} - V_p$. The strong renormalization of U_{at} to $U^{(sc)}$ is confirmed in the analyzis of the optical data [21], due to the large background dielectric constant $\varepsilon_\infty \approx 12$ which gives $\alpha_{As} \sim (10-12)$ $\mathring{A}^3$ and $U^{(sc)} \approx (1-2)$ eV. (There is also an additional non-local Coulomb term $\hat{H}_c^{(pol)}$ due to the As polarization, which depends on $V_P(\mathbf{R}_{Fe})$ and will be not studied here.)

In [20] a possible excitonic mechanism of superconductivity was analyzed in the SPS model, while the giant EPI effects were not studied at all. In the presence of *vibrations* of the As- and Fe-ions the change of $\hat{H}^{(pol)}$gives rise to an additional many-body EPI_{pol} channel with a possible huge EPI coupling potential V_{ep} where the EPI_{pol} Hamiltonian $\hat{H}_{ep}^{(pol)}(= \hat{H}_{0,ep}^{(pol)} + \hat{H}_{H,ep}^{(pol)})$ reads

$$\hat{H}_{ep}^{(pol)} = V_{ep}\sum_{\mathbf{R_{Fe}}} \hat{\varphi}_{\mathbf{R}_{Fe}}(\frac{1}{2}\hat{n}_{\mathbf{R}_{Fe}} + \hat{n}_{\mathbf{R}_{Fe}\uparrow}\hat{n}_{\mathbf{R}_{Fe}\downarrow}) \qquad (4)$$

where $V_{ep} = 4V_p(\sim 40$ $eV)$ is very large and the dimensionless phonon operator $\hat{\varphi}_{\mathbf{R}_{Fe}}$ is given by $\hat{\varphi}_{\mathbf{R}_{Fe}} \equiv [V_p(\mathbf{R}^0_{Fe} + \hat{\mathbf{u}}_{\mathbf{R}_{Fe}} - \mathbf{R}^0_{As} - \hat{\mathbf{u}}_{\mathbf{R}_{As}}) - V_p(\mathbf{R}^0_{Fe} - \mathbf{R}^0_{As})]/V_{ep}$ and $\hat{n}_{\mathbf{R}_{Fe}} = \hat{n}_{\mathbf{R}_{Fe}\uparrow} + \hat{n}_{\mathbf{R}_{Fe}\downarrow}$. Here $\hat{\mathbf{u}}_{\mathbf{R}_{Fe}}$, $\hat{\mathbf{u}}_{\mathbf{R}_{As}}$ are the displacement operators of the Fe- and As-ions, respectively. For the *harmonic EPI interaction* one has

$$\hat{\varphi}_{\mathbf{R}_{Fe}} = \frac{1}{Zd}\sum_{\mathbf{R}_{As}\epsilon n.n.\mathbf{R}_{Fe}} \mathbf{n}_{As}\cdot(\hat{\mathbf{u}}_{\mathbf{R}_{As}} - \hat{\mathbf{u}}_{\mathbf{R}_{Fe}}), \qquad (5)$$

where $\mathbf{n}_{As} = (\mathbf{R}^0_{Fe} - \mathbf{R}^0_{As})/d_{As-Fe}$. It is convenient to rewrite the Hubbard Hamiltonian $\hat{H}_{ep}^{(pol)}$in the rotational invariant form (note $2\hat{n}_{\mathbf{R}_{Fe}\uparrow}\hat{n}_{\mathbf{R}_{Fe}\downarrow} = \hat{n}_{\mathbf{R}_{Fe}} - 4\hat{\mathbf{S}}^2_{\mathbf{R}_{Fe}}/3$)

$$\hat{H}_{ep}^{(pol)} = V_{ep}\sum_{\mathbf{R}_{Fe}}\hat{\varphi}_{\mathbf{R}_{Fe}}(\hat{n}_{\mathbf{R}_{Fe}} - \lambda\hat{\mathbf{S}}^2_{\mathbf{R}_{Fe}}), \qquad (6)$$

where $\lambda = 2/3$ and the spin-like operator $\hat{\mathbf{S}} = \hat{c}^\dagger\boldsymbol{\sigma}_{\alpha\beta}\hat{c}/2$. The EPI_{pol} potential V_{ep} in Eq.(6) is large due to: (i) the large value of V_p; (ii) the rapid change of V_p with the Fe- and As-distance $d_{Fe-As}(\approx 2.4$ $\mathring{A})$, thus giving very large induced electron-phonon coupling $g_{ep}^{(pol)}(\equiv V_{ep}/d_{Fe-As}) = (4V_p)/d_{Fe-As} \sim 16$ $eV/\mathring{A}$. For comparison, the average LDA coupling constant (coming mainly from the screened lattice potential) is much smaller, i.e. $g_{ep}^{(LDA)} < 1eV/\mathring{A}$ [5]. As it is said before, the above model can be generalized to the multi-orbital case. In that case there is a summation over the orbital index in Eqs.(4,6) and there are terms due to the inter-orbital interaction. For instance, Eq.(6) reads $\hat{H}_{ep}^{(pol)} = V_{ep}\sum_{i\mathbf{R}_{Fe}}\hat{\varphi}_{\mathbf{R}_{Fe}}\{\hat{n}_{i\mathbf{R}_{Fe}} - \lambda\hat{\mathbf{S}}^2_{i\mathbf{R}_{Fe}} + \sum_{j\neq i}\hat{n}_{i\mathbf{R}_{Fe}}\hat{n}_{j\mathbf{R}_{Fe}}/2\} + \hat{H}_{nloc}$, where i,j enumerates the orbital indices while all non-local terms mentioned above are stipulated in $\hat{H}_{nloc}$. In the following we argue that the giant magneto-elastic effects in the Fe-pnictides are dominated by the EPI_{pol} effects.

Magneto-elastic coupling effects. – If the SPS model is realized in the Fe-pnictides then the part of EPI_{pol} - the second term in Eqs. (4,6), is involved in the *giant magneto-elastic effects*. It will be shown below that it gives the largest contribution to them with the following manifestations. First, in the presence of the SDW magnetic order ($S_Q \neq 0$) the Fe-pnictides show a tendency to increase significantly the c-lattice parameter (along the c-axis) in comparison to the non-magnetic ($S_Q = 0$) ”collapsed” tetragonal (cT) phase, i.e.

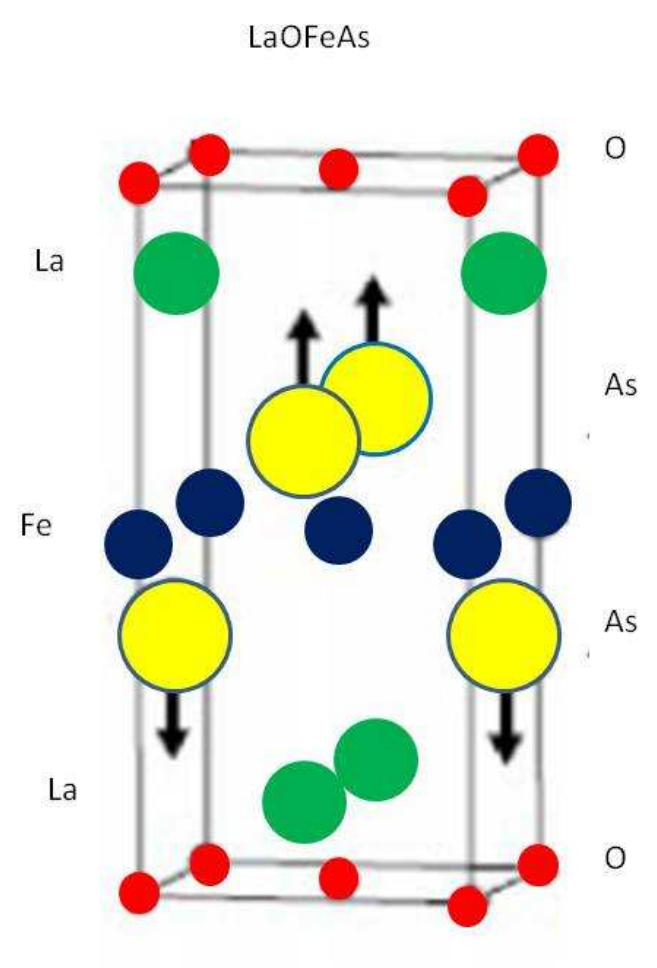

Fig. 2: Vibrations of the As-ions in A_{1g} modes of $LaOFeAs$ which produce very strong EPI_{pol}. Small displacements of the La-ions are not shown.

$c(S_Q \neq 0) > c(S_Q = 0)$. Second, recent experiments on MFe_2As_2, $M = Ca$, Sr, Ba under pressure (P) show the orthorhombic-tetragonal (the cT-phase) transition. In $CaFe_2As_2$ at $P = P_c \approx 0.4GPa$ there is a transition from the orthorhombic phase with the finite SDW order $S_Q \neq 0$) to the non-magnetic cT-phase ($S_Q = 0$) in which the superconductivity appears at $T_c = 12\ K$ [15]. This gives evidence for strong and unusual coupling of the lattice with the magnetic order. It is worth to mention that the experimental change of volume $(\Delta V/V) \approx 3 - 4\ \%$ is explained by the LDA calculations by assuming much larger critical pressure P_c than in experiments [24], i.e. $P_c^{(LDA)} = 5\ GPa \gg P_c^{(\exp)} \approx 0.4\ GPa$. The LDA magnetic pressure is given by $P_m^{(LDA)} \sim -\partial E^{(LDA)}/\partial\varepsilon$ and its small value causes that $P_c^{(LDA)} \gg P_c^{(\exp)}$, thus pointing to some missing many-body effects with much larger *magnetic pressure* (P_m) - see Eq.(7) and the analysis below it. In the following we show, that EPI_{pol} gives very large contribution to P_m - we call it the *potential magnetic pressure* $P_m^{(p)}$, thus lowering the value of P_c.

The magneto-elastic properties of the tetragonal-orthorhombic Fe-pnictides are complicated since they depend on six elastic constants, on several other magneto-elastic constants and on the magnetic free-energy. However, for our purpose to show that $P_m^{(p)} \gg P_m^{(LDA)}$ a simplified phenomenological mean-field approach is satisfactory. For the further analysis the important experimental fact is the *decrease of the* $Fe-As$ *distance* d_{Fe-As} by 1 % in the first-order phase transition, i.e. $\epsilon_d = (\delta d_{Fe-As}/d_{Fe-As}) = 0.01$. The latter lowers the "potential" energy $U_{\mathbf{R}_{Fe}}^{(sc)}$ significantly which leads to the giant magneto-elastic effects. To estimate the effect we use the experimental fact that at the critical pressure P_c the volume is changed by $3 - 4\ \%$ [15], while ϵ_d is only a part of the total strain $\varepsilon(\equiv \delta V/V) = \varepsilon_{xx} + \varepsilon_{yy} + \varepsilon_{zz}$, i.e. $\varepsilon_d \approx \varepsilon/r$ with $r \sim 3 - 4$. According to Eqs.(4-6) one has $U^{(sc)}(\delta d) = U^{(sc)} + V_{ep}\epsilon_d \approx U + 4V_p\epsilon/r$ (note $V_{ep} = 4V_p$, $V_p \sim 10\ eV$), i.e. the "potential" energy is significantly decreased under the pressure (for $\epsilon < 0$). The weak SDW magnetic order (with $S_Q \neq 0$) can be qualitatively analyzed in the Hartree-Fock (or Stoner-like) approximation with the bare spin susceptibility $\chi_0(Q) = N(0)f(Q)$, where $N(0)$ is the density of states at the Fermi level and $f(Q)$ describes the momentum dependence of the bare spin susceptibility. For $U^{(sc)}(P < P_c)\chi_0(Q) > 1$ it gives finite value for S_Q. The phenomenological Gibbs energy $G(S_Q, \varepsilon, P)$ includes: (i) the complicated elastic properties of the lattice approximately via the effective compressibility, (ii) the SDW magnetism, (iii) the magnetostriction and (iv) the effects of the applied pressure P

$$G(S_Q, \varepsilon, P) \approx \frac{\varepsilon^2}{2\kappa_{eff}} + P\varepsilon - \frac{a(\varepsilon)}{2}S_Q^2 + \frac{b}{4}S_Q^4 + \frac{c}{6}S_Q^6, \quad (7)$$

where $a(\varepsilon) = U^{(sc)}(\varepsilon) - \chi_0^{-1}(Q, \varepsilon, T)$. The first term in G is an effective lattice elastic energy with the effective compressibility κ_{eff}, while the second one is due to the work by the pressure P. The magnetic part of G contains higher order terms in S_Q^2 which are proportional to b and c since the transition may be of the first order if $b < 0$, or if $b > 0$ for $b_r = b - \kappa_{eff}(\gamma_k + \gamma_p)^2/2 < 0$ (see below), where b_r is the renormalized fourth-order coefficient in G. Note, that here we consider only effects of the *homogenous strain* on the magnetic transition in weak ferromagnets ($S_Q^2 \ll 1$) in the mean-field approximation, which can take place even very far from the critical temperature T_{sdw}. In the following we omit the temperature effects due to the strain fluctuations which are pronounced very near T_{sdw} - the Larkin-Pikin mechanism [25]. The latter may also lead to the first order transition due to the interaction of the magnetic order [25] with the share-strain fluctuations which is studied in [26]. For small strain $\varepsilon \ll 1$ one has

$$a(\varepsilon) \approx a_0 + (\gamma_k + \gamma_p)\varepsilon, \quad (8)$$

where $a_0 = [U^{(sc)} - \chi_0^{-1}(Q, 0, T)]$. The "kinetic" energy contribution to the magnetic pressure is proportional to $\gamma_k = \chi_0^{-1}(Q, 0) d\ln\chi_0(Q, \varepsilon)/d\varepsilon$, while the "potential" energy contribution to $\gamma_p = V_{ep}/r$. After the minimization of $G(S_Q, \varepsilon, P)$ (with respect to S_Q and ε) and for $b_r < 0$ the *first order phase transition* is realized at the critical pressure P_c

$$P_c = \frac{1}{(\gamma_k + \gamma_p)\kappa_{eff}}\left(a_0 + \frac{3b_{ren}^2}{16c}\right). \quad (9)$$

The SDW order parameter jumps from $S_Q \neq (3\,|b_r|\,/4c)^{1/2}$ at $P = P_c - 0$ to $S_Q = 0$ at $P = P_c + 0$. In the case of the weak first order phase transition one has $b_{ren}^2 \ll 4c$ which gives $P_c \approx a_0/(\gamma_k + \gamma_p)\kappa_{eff}$, as well as for the *second order phase transition* with $b_r > 0$

(where $S_Q = 0$ for $P = P_c - 0$). Note, the the ”kinetic” energy term γ_k in Eq. (9) is contained in the LDA band structure calculations [22], [23], [24], where it is solely responsible for the magneto-elastic effects. However, the ”potential” term γ_p which is due to the many-body EPI_{pol} effects is absent in the LDA calculations. This is the main reason that LDA gives too large value for P_c, i.e. $P_c^{(LDA)} \sim 15P_c^{(\exp)}$ [24], which implies that $\gamma_p \gg \gamma_k (\approx \gamma_{LDA})$ is realized. Indeed, in most itinerant magnets one has $\gamma_k < 2N^{-1}(0)$ and one expects similar value in the Fe-pnictides. Since $V_{ep}(\sim 40\ eV)$ is very large one has $(\gamma_p/\gamma_k) \sim 10$. The latter result implies much smaller critical pressure $P_c \ll P_c^{(LDA)}$ than the LDA predicts. This means that the giant magneto-elastic effects in the Fe-pnictides are dominated by the many-body ”potential” energy effects which are contained in EPI_{pol}. The experimental situation concerning the type of the phase transition (first- or second-order) in MFe_2As_2, $M = Ca$, Sr, Ba is still not resolved. Namely, for Ca, Sr the case $b_r < 0$ is realized while in Ba both cases $b_r > 0$ and $b_r < 0$ might be realized [15]. In spite of our limited phenomenological approach some semi-quantitative estimations are possible. For instance, one expects $\kappa_{eff} < 2 \times 10^{-2}\ (GPa)^{-1}$ [27] which gives $P_c \kappa_{eff} < 10^{-2}$ and $a_0/(\gamma_k + \gamma_p) < 10^{-2}$, $a_0/\gamma_p < 10^{-2}$. The latter condition is a constraint for the microscopic models for the SDW order parameter and the EPI_{pol} coupling.

Possible contribution of EPI_{epl} to pairing. – At present there is a confusion regarding the role of EPI in the superconducting pairing of the Fe-pnictides. In spite of numerous experiments which give appreciable evidence against gapless unconventional pairing and that the antiferromagnetic spin fluctuations are moderate in superconducting samples, the proponents of the spin fluctuation mechanism rely their believe on the small EPI calculated in the LDA calculations with $\lambda_{ep} \approx 0.2$ and $T_c \sim 1\ K$ [5]. However, like in the case of high-temperature superconductors (HTSC), heavy fermions and organic superconductors, etc. the LDA calculations fail whenever many body effects play important role. For instance, in case of HTSC numerous tunnelling, transport and neutron scattering measurements point to a strong EPI, while various LDA calculations furnished diversity of values for λ_{ep}, from $0.2 - 1$ - see discussion in [28]. The situation is similar in Fe-pnictides where LDA cannot explain quantitatively even the magnetic and structural properties, let alone the EPI effects and superconductivity. Here, we give some qualitative estimate of the *polarization induced* EPI which is described by $\hat{H}_{ep}^{(pol)}$ in Eq.(6) and not contained in LDA.

The strongest EPI_{pol} coupling is for the A_{1g}-modes (there are at least two such modes) where the As-ions vibrate along the c-axis as shown in Fig.2. These modes contribute mainly to the *intra-band pairing*. At present we can only estimate the intra-band ($i = e, h$) bare coupling constants $\lambda_{ep,A_{1g}}^{0,i} = 2N_i(0) g_{A_{1g}}^2/\omega_{A_{1g}}$ with $g_{A_{1g}}^2 \approx V_{ep}^2 \cos^2\theta \left\langle \hat{u}_{As}^2 \right\rangle / d_{Fe-As}^2$. Here, $\omega_{A_{1g}}$ is the energy of an A_{1g}-mode, $N_i(0)$ is the (intra-band) density of states, $\left\langle \hat{u}_{A_{1g}}^2 \right\rangle$ is the average of the quadratic As-displacement, θ is the angle between $\mathbf{n}_A$ and the c-axis. In the approximation of one-phonon processes one has $\left\langle \hat{u}_{A_{1g}}^2 \right\rangle \approx \hbar^2/2M_{As}\omega_{A_{1g}}$ where M_{As} is the atomic mass of the As-ion. For $\omega_{A_{1g}} \approx 25\ meV$ [29] and $N_i(0) \approx 0.5\ states/eV \cdot spin$ (note that $N_e(0) \sim N_h(0) \sim N(0)$) one obtains $\lambda_{ep,A_{1g}}^{0,i} \approx 0.7$. The estimated $\lambda_{ep,A_{1g}}^{0,i}$ is rather large giving a hope that the real (renormalized) coupling $\lambda_{ep,A_{1g}} (< \lambda_{ep,A_{1g}}^{0,i})$, might be also appreciable. In order to calculate $\lambda_{ep,A_{1g}}^{i}$ one should correctly take into account the matrix elements of $g_{A_{1g}}$ in the band-basis, screening effects, etc. Even if $\lambda_{ep,A_{1g}}^{i} \approx 0.3$ this would give an appreciable total intra-band coupling constant $\lambda_{ep,A_{1g}} = 2\sum_i \lambda_{ep,A_{1g}}^{i} \sim 1$ thus contributing significantly to the effective pairing constant λ_{eff} - see [13].

In [30] was proposed that the Fe-breathing mode may give appreciable EPI due to the change of the Fe-Fe hopping energy in this mode. However, the latter effects are not considered here. In that respect, we point out that the linear (in the displacement $\mathbf{u}_{Fe}$) contribution of the Fe-breathing mode to EPI_{pol} vanishes due to the symmetry reasons - see Fig.2, but this mode gives very *large nonlinear EPI_{pol} coupling* (with $\hat{\varphi}_{\mathbf{R}_{Fe}} \sim \mathbf{u}_{Fe}^2$) due to the large value of $\partial^2 V_{ep}/\partial d_{Fe-As}^2$ - see Eq.(3). The large nonlinear EPI_{pol} coupling is the strongest in the Fe-breathing mode and its effect on superconductivity and magneto-elastic properties might be also important.

Conclusions. – We have analyzed a possibility for an appreciable many-body contribution to the electron-phonon interaction (EPI) in the Fe-pnictides, which is due to the electronic polarization of the As- ions in the presence of charge fluctuations on the Fe-ions which is proposed in [20]. In that case the polarization induced EPI_{pol} potential $V_{ep} \sim 40\ eV$ is especially large for vibrations of the As-ions and depends strongly on the As-Fe distance d_{As-Fe}, i.e. $V_{ep} \sim d_{As-Fe}^{-4}$. The corresponding EPI_{pol} coupling $g_{ep}^{pol} (= \partial V_{ep}/\partial d_{As-Fe})$ is much larger than the one obtained in the LDA band structure calculations, i.e. $g_{ep}^{pol} \gg g_{ep}^{(LDA)}$ with $g_{ep}^{pol} (\sim 16\ eV/\mathring{A}) \gg g_{ep}^{(LDA)} (< 1\ eV/\mathring{A})$. The latter may significantly contribute to the *intra-band s-wave pairing* with the bare coupling constant $\lambda_{ep,A_{1g}}^{0} \sim 1$, thus disfavoring any gapless unconventional intra-band superconductivity. As the result an appreciable positive As-isotope effect in the superconducting critical temperature is expected. The EPI_{pol} channel gives very strong nonlinear coupling in the Fe-breathing mode, which might be important for superconductivity and additional magneto-elastic effect.

The electron-lattice coupling EPI_{pol} gives much larger contribution to the magnetic pressure than the LDA calculations predict, thus giving rise to the giant magneto-elastic effects in the transition from the magnetic to the non-magnetic state under pressure in MFe_2As_2, $M = Ca$, Sr, Ba. The critical pressure P_c for the magnetic and structural phase transition is dominated by the "potential" energy contribution EPI_{pol} in the magnetic pressure, while the LDA "kinetic" energy effects are much smaller. EPI_{pol} is expected to be important in other Fe-based superconductors which contain highly electronically polarizable ions such as Se, Te, S etc. It might be operative also for some oxygen modes in high-temperature superconductors due to the appreciable electronic polarizability of the O^{2-}-ions.

REFERENCES

[1] Kamihara Y *et al.*, *J. Am. Chem. Soc.* **130** (2008) 3296
[2] Ren Z.-A *et al.*, *Chin. Phys. Lett.* **25**, (2008) 2215
[3] Wu G*et al.*, *arXiv:*0811.0761v2.
[4] Rotter M, Tegel M, and Johrendt D, *Phys. Rev. Lett.* **101** (2008) 107006
[5] Boeri L, Dolgov OV and Golubov AA, *Phys. Rev. Lett.* **101** (2008) 026403
[6] Mazin II *et al.*, *Phys. Rev. Lett.* **101** (2008) 057003
[7] Korshunov MM *et al.*, *Phys. Rev. B* **78** (2008) 140509(R)
[8] Qiu Y *et al.*, *Phys. Rev. B* **78** (2008) 052508
[9] Lumsden MD *et al.*, *Phys. Rev. Lett.* **102** (2009) 107005
[10] Grafe HJ *et al.*, *arXiv:* 0811.4508v2 (2009)
[11] Nakai Y *et al.*, *arXiv:* 0810.3569v1 (2008)
[12] Kulić ML and Dolgov OV, *Phys. Rev. B* **60** (1999) 13062
[13] Kulić ML, Drechsler SL and Dolgov OV, *EPL* **85** (2009) 47008
[14] Fuchs G *et al.* , *Phys. Rev. Lett.* **101** (2008) 237003
[15] Kreyssig A *et al.*, *Phys. Rev. B* **78** (2008) 184517
[16] Liu RH *et al*, *arXiv:*0810.2694v1 (2008
[17] Shirage PM *et al*, *arXiv:*0903.3515v1 (2009)
[18] de Boer DKG *et al.*, *Phys. Rev. B* **29** (1984) 4401
[19] Sawatzky GA *et al.*, *Phys. Rev. Lett.* **75** (1995) 4658
[20] Sawatzky GA *et al.*, *arXiv:*0808.1390v1 (2008)
[21] Drechsler SL *et al.*, *arXiv:*0904.0827v1 (2009)
[22] Yildirim T, *Phys. Rev. Lett.* **102** (2009) 037003
[23] Yndurain F and Soler JM, *Phys. Rev. B* **79** (2009) 134506
[24] Zhang YZ *et al.*, *arXiv:*0812.2920v2 (2009)
[25] Larkin AI and Pikin SA, *Sov. Phys. JETP* **29** (1969) 891
[26] Barzykin V and Gor'kov LP, *Phys. Rev. B* **79** (2009) 134510
[27] Shein IR and Ivanovskii AL*, Scripta Mater.* **59** (2008) 1099
[28] Kulić ML, *Phys. Rep.* **338** (2000) 1;
[29] Hadjiev VG *et al.*, *arXiv:*0804.2285v1 (2008)
[30] Eschrig H, *arXiv:*0804.0186v2 (2008)